


Thread spec. (S02)
17E [ISO11363-1 (UN)]
25E [ISO11363-1 (UN)]
W21.8mm×1/14" [DIN477 N°6]
25T [BS341-1991 (GB)]
1×14BS [BS341-1991 (GB)]
3/4"-14NGT [- ANSIB57.1]
3/4-14NPSM [ASME B1.20.1-2013]
M25×2 (25P) [ISO15245-1]
★ D. Neck ≥ Tmin×2 + Thread Max. major diameter
★ More thread spec. are available

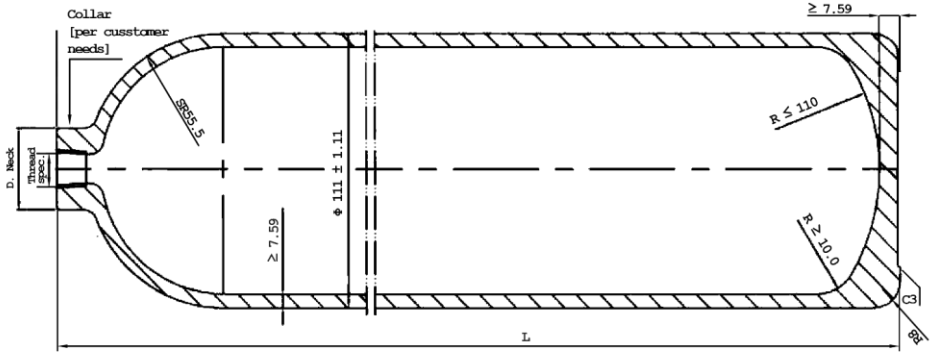

Schematic diagram of bottle mouth cone thread

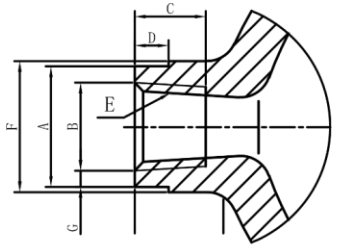

Schematic diagram of bottle mouth straight thread

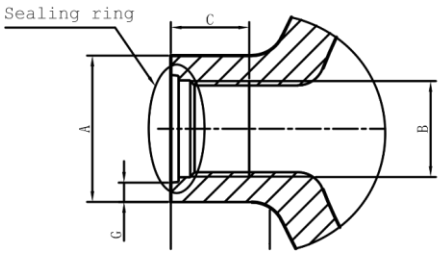

	Name
A	Outer diameter of bottle mouth
B	Large diameter of thread base
C	Thread depth
D	Height of steps
E	Thread taper
F	Outer diameter
G	Wall thickness (not less Tmin)

Note: ★Customers can freely choose thread models that meet different thread standards. Correspondingly, the thread parameters in the chart will also change.
★The size of the straight thread sealing groove is related to the valve structure, which is usually provided by the customer, or designed according to the valve structure drawings provided by the customer.

WORKING PRESSURE TO (PW/PS)	P.W.	
	Bar	psi
	207	3000

TEST PRESSURE (PH/PT)	P.H.	
	Bar	psi
	310.5	4503

BURST PRESSURE min (P.B.)	P.B.	
	Bar	psi
	496.8	7205

MODEL	WATER CAPACITY -0/+5% LITERS	LENGTH "L" ±20mm MM	APPROX. WEIGHT -5/+10% KG	PED CATEGORY (GROUP 1 GASES)	
HPAL20.7H-111(7.59)-S02-1L	1.0	220	2.1	III	← Vmin
HPAL20.7H-111(7.59)-S02-3L	3.0	500	4.1	III	← Type
HPAL20.7H-111(7.59)-S02-4L	4.0	640	5.0	III	← Vmax

Note:
Model HPAL20.7H-111(7.59)-S02-3L is the design qualification test cylinder. Vmin and Vmax represent the range covered by the same design family.

HPAL20.7H-111(7.59)-S02-1.5L	1.5	290	2.6	III	
HPAL20.7H-111(7.59)-S02-1.9L	1.9	346	3.0	III	
HPAL20.7H-111(7.59)-S02-2L	2.0	360	3.1	III	← Variants
HPAL20.7H-111(7.59)-S02-2.5L	2.5	430	3.6	III	
HPAL20.7H-111(7.59)-S02-2.7L	2.7	458	2.7	III	
HPAL20.7H-111(7.59)-S02-3.5L	3.5	570	4.6	III	

TECHNICAL REQUIREMENTS

1	DESIGN SPECIFICATION(S):	***EN ISO 7866:2012 + A1:2020***
2	SUPERVISING PROVISION(S):	***ADR/RID 2021 & DIRECTIVE 2010/35/EU (TPED)*** ***ADR/RID 2021 & DIRECTIVE 2014/68/EU (PED)***
3	Min./Max. allowable temperature, Tsmax/min:	***-40℃ to +65℃***

4 Material: ***AA6061*** CHEMICAL COMPOSITION (%)

Si	Fe	Cu	Mn	Mg	Cr	Zn
0.40~0.80	***MAX.0.70***	*0.15~0.40*	***MAX.0.15***	*0.80~1.20*	*0.04~0.35*	***MAX.0.25***

Ti	Pb	Bi	Other each	Other total	Al
MAX.0.15	***MAX.0.003***	***MAX.0.003***	***MAX.0.050***	***MAX.0.150***	***Remain***

5 Heat treatment: solution ***540 ±10℃*** for ***120±36 min***
ageing ***180 ±5℃*** for ***480±96 min***

6 CYLINDER MACHANICAL PROPERTIES AT ROOM TEMPERATURE, AFTER HEAT TREAMENT:

YIELD [MPa]	TENSILE [Mpa]	ELONG A [%]	Hardness
280	***325***	***≥ 12***	***90~125 [HB]*** ***76~45 [HBR]***

7 ***The body of the bottle shall be free of wrinkles, deformations, and visible cracks that would affect strength.***

8 Filling content: For DIRECTIVE 2010/35/EU (TPED): see "Filling Gas Table-HPAL20.7H-S02-GASES"
For DIRECTIVE 2014/68/EU (PED): diving breathing gas group 1.

9 ***Corrosion allowance: 0 mm.***

10 ***Pressure-cycling test:The gas cylinders to successive reversals the hydraulic test pressure.The gas cylinders shall withstand 12000 cycles without failure.***

11 ***The inner and external surface shall be free of any cracks and the defects shown in ISO10461 annex B table B.1 and B.2.***

12 ***The out-of-roundness of the cylindrical shell shall not exceed 2% of the diameters,the straightness of the cylindrical shell shall not exceed 3% and the vertical shall not exceed 10%.***

SINOGES INDUSTRY EQUIPMENT (WUHAN) CO., LTD.

DESCRIPTION	**REFILLABLE SEAMLESS ALUMINIUM CYLINDER FOR COMPRESSED, LIQUEFIED, AND DISSOLVED GASES**

SCALE	NOT TO SCALE		DRAWING NUMBER	HPAL20.7H-111(7.59)-S02
DRAWN BY	刘高越	2023-05-19		
CHECKED BY	但煜婧	2023-05-19	REV.	01
APPROVED BY		2023-05-19	SHEET NO. 1	OF 1 SHEET(S)

This drawing is the property of Sinoges Industry Equipment (Wuhan) Co., Ltd.
Unauthorized disclosure to any third party or duplication is not permitted.

This drawing is the property of Sinoges Industry Equipment (Wuhan) Co., Ltd.
Unauthorized disclosure to any third party or duplication is not permitted.



★ Where:

3/4-14NPSM	Identification of cylinder thread;
CN	Country of origin;
SINOGES	Manufacture's identification;
XXXXXXXXX	Serial No.;
AA6061 T6	Material of cylinder;
H	Only for contents with a risk of hydrogen embrittlement;
7.59MM	Minimum guaranteed wall thickness;
XX.XKG	Empty weight of cylinder;
XX.XL	Actual water capacity of cylinder;
PW207	Max. service pressure (NOT NEEDED FOR FILLING LIQUID GAS SUCH AS CO2);
PH310.5BAR	Hydraulic test pressure;
TAREXX.XKG	Tare weight (optional);
X.XXKG_XXX	Weight & name of gas to be filled (OPTIONAL);
TXXXX	CE mark and the ID of notified body;
-40℃	Service Temperature (optional);
EN ISO 7866	Applied Standard;
P	Country of approval;
○	The inspector's mark;
20XX/XX	Date of initial inspection (year/month);

STAMP MARKINGS ACCORDING TO ADR/RID 2021 & DIRECTIVE 2010/35/EU (TPED)



★ Where:

M25×2	Identification of cylinder thread;
CN	Country of origin;
SINOGES	Manufacture's identification;
XXXXXXXXX	Serial No.;
AA6061 T6	Material of cylinder;
CAT.III	Category of the pressure vessel;
7.59MM	Minimum guaranteed wall thickness;
XX.XKG	Empty weight of cylinder;
XX.XL	Actual water capacity of cylinder;
PW207	Max. service pressure;
PH310.5BAR	Hydraulic test pressure;
DIVING_BREATHING_GAS_GR.1	Gas name and gas group;
CEXXXX	CE mark and the ID of notified body;
TS -40/65℃	Service Temperature (optional);
EN ISO 7866	Applied Standard;
P	Country of approval;
○	The inspector's mark;
20XX/XX	Date of initial inspection (year/month);

STAMP MARKINGS ACCORDING TO ADR/RID 2021 & DIRECTIVE 2014/68/EU (PED)

Note:
Each "_" in the stamped picture shown is a space between characters, and there is no need to type any content in actual production.
所示钢印图中每一个“_”为一个字符间距的留空，实际生产中不用打任何内容。

SINOGES INDUSTRY EQUIPMENT (WUHAN) CO., LTD.

DESCRIPTION	**STAMP MARKING OF REFILLABLE SEAMLESS STEEL CYLINDER FOR COMPRESSED, LIQUEFIED, AND DISSOLVED GASES**			
SCALE	NOT TO SCALE		DRAWING NUMBER	HPAL20.7H-111(7.59)-S02-STP
DRAWN BY	冯高越	2023-05-19		
CHECKED BY	但煜婧	2023-05-19	REV.	01
APPROVED BY	吴晓燕	2023-05-19	SHEET NO. 1	OF 1 SHEET(S)